



# Cold Rolled Steel

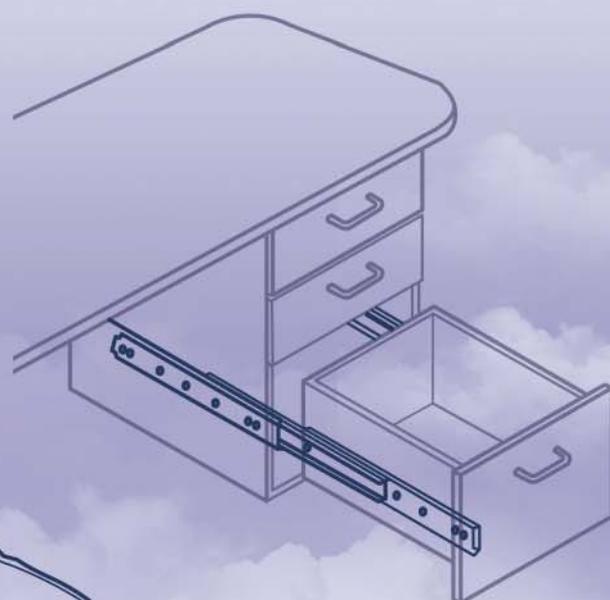

## The quality policy of China Steel Corporation

China Steel Corporation, based-on customer orientation, will incessantly innovate, research & develop to provide excellent and eco-friendly products, and consequently fulfill our responsibility to society.

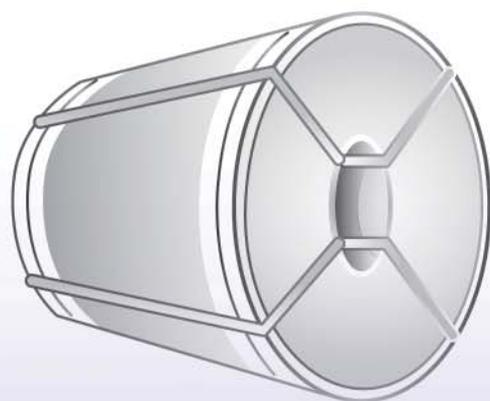

China Steel Building (Group Headquarters)



1	1. Brief Introduction
2	2. Product and Service Features
3	3. Introduction of New Products
5	4. Certification
7	5. Manufacturing Process and Major Equipments
10	6. Application Examples
11	7. Specification
11	7.1 Chemical Composition and Mechanical Properties
19	7.2 Tolerances
26	7.3 Classifications of Quality
27	8. Product Availability
28	9. Marking and Packing
29	10. Precautions for Use
32	11. Conversion Tables
35	12. Comparison of Specification
37	13. Ordering Information

Reversing Cold Mill



A NAME FOR QUALITY,  
TECHNOLOGY AND SERVICE

## CHINA STEEL

China Steel Corporation (CSC), located at Kaohsiung, Taiwan was founded in December 1971. With annual capacity (in terms of crude steel) around 10 million tonnes, CSC produces a range of products that includes plates, bars, wire rods, hot and cold rolled coils, electrogalvanized coils, electrical steel coils, hot-dip galvanized coils, and Ti/Ni-base alloy. The domestic market takes roughly 65% of CSC's production and the exports take the remaining 35%. CSC is the largest steel company in Taiwan, enjoying more than 50% of the domestic market. Major export destinations are Mainland China, Japan and Southeast Asia.

CSC is very active in innovation, and has strong capability to put the innovations into practice. The company's vision is: "We aspire to be a trustworthy steel company of global distinction that pursues growth, environmental protection, energy saving and value-innovation". CSC actively puts into practice its corporate values of "teamwork, entrepreneurial approach, down-to-earthiness and pursuit of innovation", as well as its operations beliefs of "promotion of social well-being, result orientation, implementation of teamwork, and emphasis on employees' self-realization." CSC keeps deepening the roots for its core business in steel, and devoted to integrate the related downstream industries to foster healthy development and international competitiveness of Taiwan's steel related industry.



Plant Greening





China Steel Corporation (CSC) is an integrated steel producer. After its phase II expansion construction was completed on June 30, 1982, CSC launched its production of Cold Rolling Mill. Subsequently, CSC went through to complete its phases III and IV expansion constructions. Products include cold-rolled coils, magnetic steel coils, electro-galvanized coils, hot-dip galvanized coils and color coils. This manual introduces cold rolled coils only.

CSC's Cold Rolling Mill has numerous and complete production lines. Through unceasing developments and improvements over the years, cold rolled coils are diversified from narrow to wide, thin to thick, soft to hard and dull to bright. The available thickness of cold-rolled coils can be provided is 0.20 ~ 3.20mm, and available width is 780 ~ 1830mm. They are available for various processing uses and have been sufficient to meet the requirements of industries, such as forming soft steels, high strength steel sheets with improved formability for automobile structures, automobile structure steels with high strength dual-phase, steel sheets for fine blanking, steel sheets for slide rails, decarburized steel sheets and strips for porcelain enameling, as well as cold-rolled medium carbon steels, high carbon steels, alloy steels and special steel strips, etc.

Through the integrated quality management of iron making, steelmaking and steel rolling to the release and shipping of finished products, CSC's cold-rolled steel products are excellent in their internal and external quality, dimensional accuracy and processing properties, as well as have been approved for various related certifications such as ISO 9001, ISO/TS16949, JIS MARK, and IECQ QC080000 (Hazardous Substance Process Management). They meet

the regulations of RoHS (Restriction of Hazardous Substances Directive) and REACH (Registration, Evaluation, Authorization and Restriction of Chemical substances), and are verified through Certification of high-strength grades by the well-known carmakers. The quality is good enough to meet customers' needs.

The vision of CSC's customer services is to gain customers' appreciation and trust and help them be successful, and the aim of that is to promote customers' technology and upgrade the steel industry. In order to enhance the customer services, CSC adopts multi-step and multi-level service pattern which is characterized by emphasizing on (1) the pre-sale services for helping customers to choose suitable materials and improve their production processes; (2) handling complains and claims from customers with proper and rapid manner, and conducting customers the corresponding improvements to the root-causes; (3) providing customers with the developed high-grade materials to meet the upgrade policy for domestic industries.

The stable and reliable quality of CSC's steel products have gained the acceptance of domestic industries widely, and CSC has also been selected as the first priority provider to purchase their needed steel materials owing to CSC's quick and efficient technical services. CSC will continue to improve customer services and the technical technologies both for customers and CSC itself to promote steel-use industries' international competitiveness.

### **JFS JSC980Y Ultra-high strength structural steel for automobile**

The tensile strength of this grade could reach 980 MPa above by formation of dual phase structure which combines the ductile ferrite and high strength martensite. By characteristics with high strength and superior ductility, this is an important material for light-weighted energy saving automobile design including application for safety structural parts, bumper, seat skid parts, etc.

### **EN HC420LA High strength low alloy (HSLA) structural steel**

The yield strength of this grade could reach 420 MPa above in adoption of HSLA type steel structure which shows the high yield ratio, fine work formation and weldability. This is also an important material for light-weighted energy saving automobile design.

### **JFS JSC340H High strength baked-hardening (BH) steel**

The tensile strength of this grade could reach 340 MPa above which processes the character of fine stamping formation and baked hardening. The material could be served as light-weighted energy saving automobile part such as outer panel or body construction which is strengthened after coating baked treatment.

---

## **SAE 1552**

SAE1552 belongs to high manganese carbon steel with excellent cleanness and high strength after suitable heat treatment. The characteristics of this product fit in with requirements of manufacturing timing chain of automobile engine.

---

## **JIS G3311 SKS51M**

SKS51M belongs to alloy tool steel with high hardness, high strength, great flatness and suitable for application of saw blade.

---

## **CSC CC8660**

CSC CC8860 belongs to nickle chrome molybdenum steel with excellent anti-abrasion, anti-impact, anti-deformation and can be applied to chain saw for lumbering.

---

## **JIS G3125 SPA-C**

JIS G3125 SPA-C is superior atmospheric corrosion resisting cold rolled steel and can be used in environment containing sulfuric waste gas.




ISO 9001 Certificate




ISO/TS 16949 Certificate



IECQ Certificate

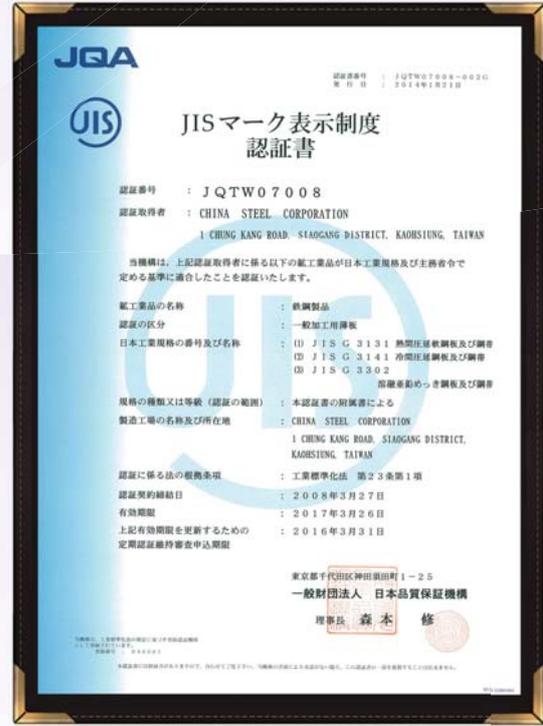

JIS MARK 07008 Certificate

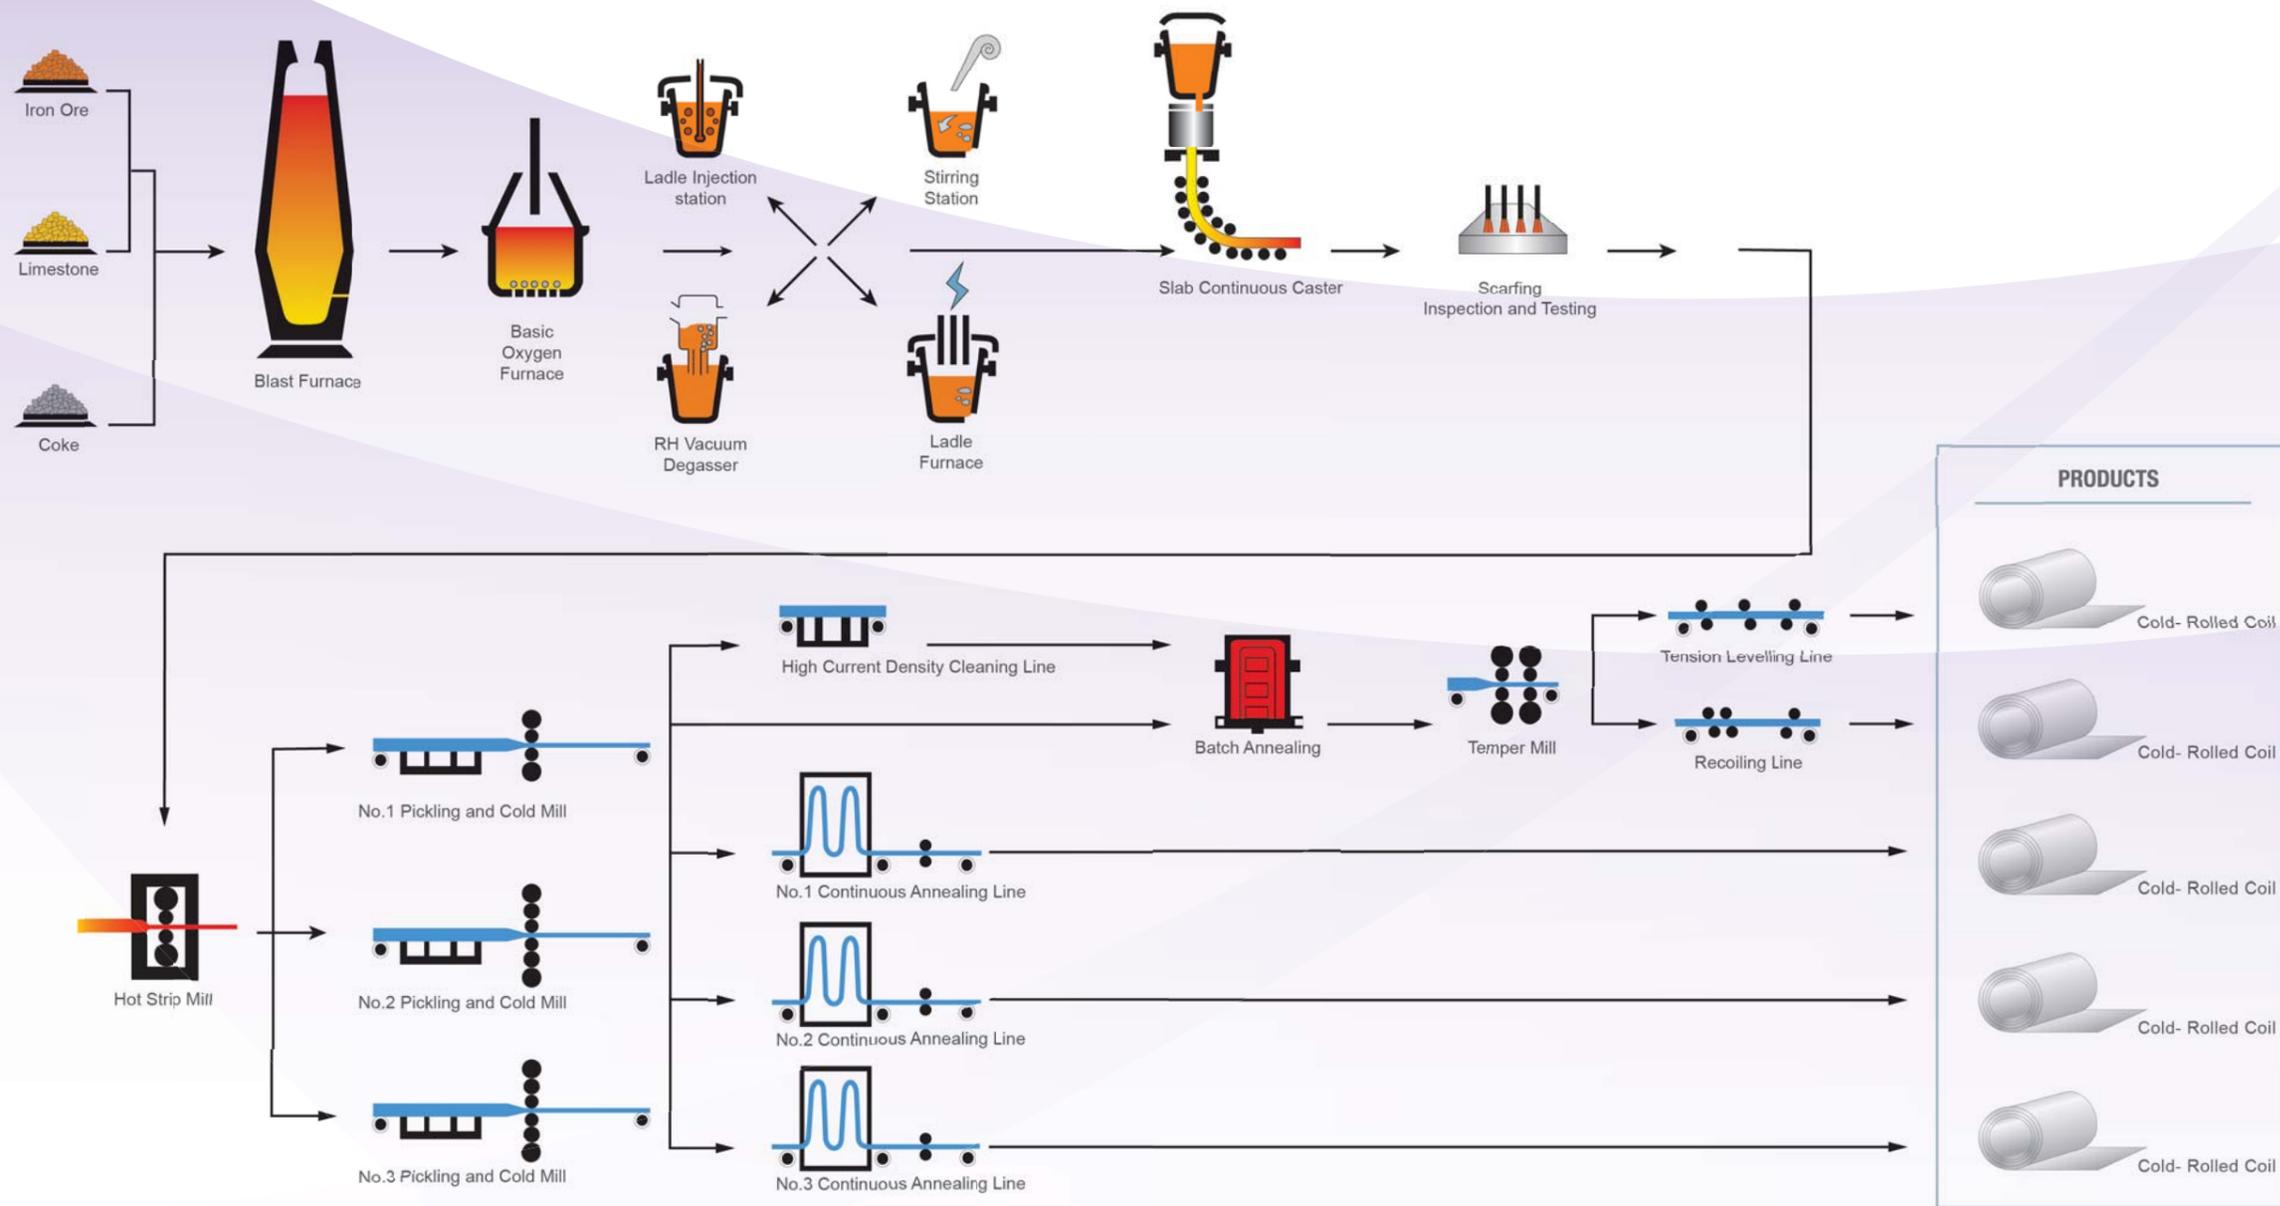


### Pickling



The main purpose of this stage is to remove the scale of hot rolled coil by heated solution of hydrochloric acid for its smooth surface finish.

### Cold rolling

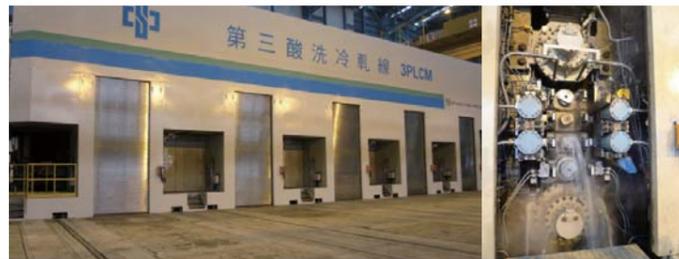

The pickled coils are rolled into specified thickness by cold rolled mills with controlled rolling force and strip tension. Based on strip center and edge part measurements of the thickness at the entry and delivery sides of the mills, either the strip center or edge thickness deviation is minimized by the computer-controlled system.

### Annealing



The steel strip is significantly hard and brittle after cold rolling which the grains are elongated along with lots strain energy. To obtain the desired mechanical properties of strip, the coils shall be piled and covered by the box which called batch annealing or the strip is continuous treated in furnace which called continuous annealing. Both annealing technology are possessed in CSC according to different product requirements.

### Temper Rolling




After the annealing, the strip is slightly rolled by the skin-pass mill to avoid the common defect called stretcher strain and adjusting mechanical properties. The strip surface roughness is also determined by this stage.


### Finishing and Inspection



The entire coil strip thickness, width and surface quality are checked by automatic inspection system and well-trained inspectors in this stage. After the oil applied over strip surface, the product coil is cut into specified mass.

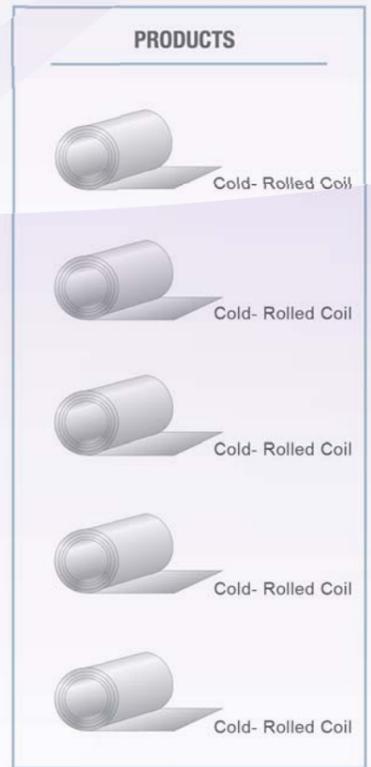


### Edge Drop Measurement(EDM) System

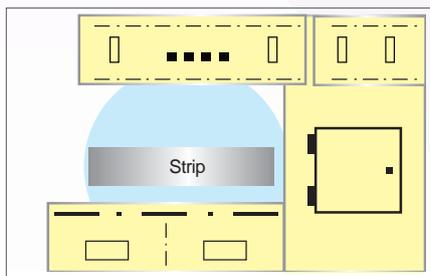


The thickness deviation with the whole coil is automatically inspected by the X-ray generated system to assure the thickness accuracy.

### Shape-meter Roll

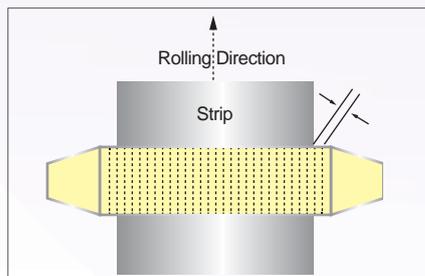

The rolling controlled could be dynamically adjusted depending on the simultaneous measurement result of strip flatness by shape-meter roll.

### Automatic Surface Inspection System

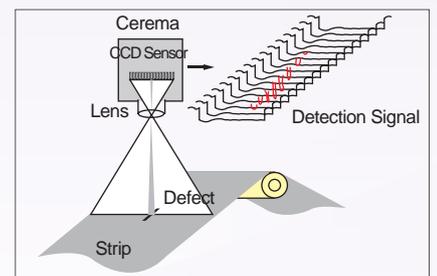

Both sides of strip surface with entire coil length are automatically inspected by the high resolution camera system to assure the strip surface quality.



Automobile



Seats of Automobile



Slide



Metal Ceiling



Compartment Assembling



Containers

## 7.1 Chemical Compositions and Mechanical Properties

### 7.1.1 Carbon Steel Sheet for of Forming Fabrication

(1) JIS G3141-2011 SPCC/SPCD/SPCE/SPCF/SPCG (-SD, Standard temper)

Specification			JIS G3141					
Symbol of Grade			SPCC	SPCCT <sup>(NOTE 2)</sup>	SPCD	SPCE	SPCF	SPCG
Chemical Composition %	C max.		0.15		0.10	0.08	0.06	0.02
	Mn max.		0.60		0.50	0.45	0.45	0.25
	P max.		0.100		0.040	0.030	0.030	0.020
	S max.		0.035		0.035	0.030	0.030	0.020
	Si max.		—		—	—	—	—
Tension Test	Tensile Strength N/mm <sup>2</sup> min.	0.25 ≤ t	—	270	270	270	270	270
	Yield Point N/mm <sup>2</sup> max.	0.25 ≤ t	—	—	(240)	(220)	(210)	(190)
No.5 test piece	Elongation % min.	0.25 ≤ t < 0.30	—	28	30	32	—	—
		0.30 ≤ t < 0.40	—	31	33	35	—	—
rolling direction		0.40 ≤ t < 0.60	—	34	36	38	40	42
Thickness (t) mm		0.60 ≤ t < 1.00	—	36	38	40	42	44
		1.00 ≤ t < 1.60	—	37	39	41	43	45
		1.60 ≤ t < 2.50	—	38	40	42	44	46
		2.50 ≤ t	—	39	41	43	45	—
The average ratio of plastic strain $\bar{\epsilon}$	0.50 ≤ t ≤ 1.00	—	—	—	—	—	1.5min.	
	1.00 < t ≤ 1.60	—	—	—	—	—	1.4min.	
Bend Test No.3 test piece rolling direction	Bend Angle		( 180° )					
	Inside Clearance		Flat on Itself					

Notes : 1. Alloying elements other than those in the above table can be added as necessary.

2. For SPCC that guarantees tensile strength and elongation.

Remarks : 1. For those less than 0.60 mm in thickness, as a rule, the tension test shall be omitted.

2. SPCF and SPCG shall be guarantees for non-ageing property for six months after shipment from the manufacturer's factory.

3. The upper limit of yield point or proof stress in parenthesis is informative and can be applied when agreed upon between the purchaser and the supplier.

## (2) JIS G3141-2011 SPCC - 1D/2D/4D/8D

Specification		JIS G3141			
Classification		SPCC-1D	SPCC-2D	SPCC-4D	SPCC-8D
Hardness	HRB	85 min.	74~89	65~80	50~71
	HV	170 min.	135~185	115~150	95~130
Bend Test	Bend Angle	—	180°		
	Inside Clearance	—	Thickness×2.0	Thickness×1.0	Flat on Itself

Notes : As to hardness, either HRB or HV shall be applied.

(3) JIS G3141 SPCG-SD MR (Improve  $\bar{r}$ )

Symbol of Grade	Thickness (t) mm	Tensile Strength N/mm <sup>2</sup>	Yield Point N/mm <sup>2</sup>	Elongation %	$\bar{r}$
SPCG-SD	0.60 ≤ t < 0.80	270 min.	175max.	46min.	1.8min.
	0.80 ≤ t < 1.00		165max.	47min.	
	t = 1.00		155max.	48min.	

## (4) ASTM A1008-2012

Symbol of Grade		CS Type			DS Type		DDS <sup>F,G</sup>	EDDS <sup>J</sup>
		A <sup>D,E,F,G</sup>	B <sup>D</sup>	C <sup>D,E,F,G</sup>	A <sup>E,I</sup>	B		
Chemical Composition %	C	0.10max.	0.02~0.15	0.08max.	0.08max.	0.02~0.08	0.06max.	0.02max.
	Mn max.	0.60			0.50		0.50	0.40
	P max.	0.030		0.100	0.020		0.020	0.020
	S max.	0.035			0.030		0.025	0.020
	Al min.	... <sup>A</sup>			0.01	0.02	0.01	0.01
	Si	... <sup>A</sup>						
	Cu max.	0.20 <sup>H</sup>			0.20		0.20	0.10
	Ni max.	0.20			0.20		0.20	0.10
	Cr max. <sup>B</sup>	0.15			0.15		0.15	0.15
	Mo max.	0.06			0.06		0.06	0.03
	V max.	0.008			0.008		0.008	0.10
	Nb max.	0.008			0.008		0.008	0.10
	Ti max. <sup>C</sup>	0.025			0.025		0.025	0.15
	N	... <sup>A</sup>						
	B	... <sup>A</sup>						
Bend Test	Bend Angle	180°						
	Radius of Inside Surface	Flat on Itself						

Remarks : A. Where an ellipsis(...) appears in the table, there is no requirement, but the analysis result shall be reported.

B. Chromium is permitted, at the purchaser's option, to 0.25 % maximum when the carbon content is less than or equal to 0.05 %.

C. For steels containing 0.02 % or more carbon, titanium is permitted at the producer's option, to the lesser of 3.4N+1.5S or 0.025 %.

D. When an aluminum deoxidized steel is required for the application, it is permissible to order commercial steel (CS) to a minimum of 0.01 % total aluminum.

E. Specify Type B to avoid carbon level below 0.02 %.

F. It is permissible to furnish as a vacuum degassed or chemically stabilized steel, or both, at the purchaser's option.

G. For carbon contents less than or equal to 0.02 %, it is permissible to use vanadium, columbium or titanium, or a combination thereof, as stabilizing elements at the purchaser's option. In such cases, the applicable limit for vanadium or columbium shall be 0.10 % max. and limit for titanium shall be 0.15 % max.

H. When copper steel is specified, the copper limit is a minimum requirement. When copper steel is not specified, the copper limit is a maximum requirement.

I. If produced utilizing a continuous anneal process, stabilized steel is permissible at the producer's option, and Footnotes F and G apply.

J. Shall be furnished as vacuum degassed and stabilized steel.

(5) EN 10130- 2006

Symbol of Grade		DC01	DC03	DC04	DC05	DC06
Chemical Composition %	C max.	0.12	0.10	0.08	0.06	0.02
	Mn max.	0.60	0.45	0.40	0.35	0.25
	P max.	0.045	0.035	0.030	0.025	0.020
	S max.	0.045	0.035	0.030	0.025	0.020
	Ti max.	—	—	—	—	0.3 <sup>(2)</sup>
Tension Test	Tensile Strength MPa	270~410	270~370	270~350	270~330	270~330
	Proof Stress MPa max.	280	240	210	180	170
Type 2 test piece	Elongation % min.	28	34	38	40	41
Perpendicular to rolling direction	ratio of plastic strain $r_{90}$ min.	—	1.3	1.6	1.9	2.1
	tensile strain hardening exponent $n_{90}$ min.	—	—	0.180	0.200	0.220

Notes : 1. 1MPa=1 N/mm<sup>2</sup>

- Titanium may be replaced by niobium. Carbon and nitrogen shall be completely bound.
- When the thickness is less than or equal to 0.7 mm and greater than 0.5 mm, the minimum value for elongation is reduced by 2 units. For a thickness less than or equal to 0.5 mm, the minimum value is reduced by 4 units.
- The values of  $r_{90}$  and  $n_{90}$  only apply to products with a thickness equal to or greater than 0.5 mm.
- When the thickness is over 2 mm, the value for  $r_{90}$  is reduced by 0.2.
- For design purposes the lower limit of Yield Proof Stress for grades DC01, DC03, DC04 and DC05 may be assumed to be 140 MPa.

## 7.1.2 High Strength Steel Sheets with Improved Formability for Automobile Structural Uses

(1) JIS G3135-2006

Symbol of Grade	Tension Test				Bend Test			
	Tensile Strength N/mm <sup>2</sup>	Proof Stress N/mm <sup>2</sup>	Elongation %		Test Piece	Bend Angle	Radius of Inside surface	Test Piece
			Thickness (t) mm					
			0.6 ≤ t < 1.0	1.0 ≤ t ≤ 2.3				
SPFC340	340min.	175min.	34min.	35min.	JIS No.5 Perpendicular to rolling direction	180°	JIS No.3 Perpendicular to rolling direction	Flat on itself
SPFC370	370min.	205min.	32min.	33min.				Flat on itself
SPFC390	390min.	235min.	30min.	31min.				Flat on itself
SPFC440	440min.	265min.	26min.	27min.				Flat on itself
SPFC490	490min.	295min.	23min.	24min.				Flat on itself
SPFC540	540min.	325min.	20min.	21min.				Thickness × 0.5
SPFC590	590min.	355min.	17min.	18min.				Thickness × 1.0
SPFC490Y	490min.	225min.	24min.	25min.				Flat on itself
SPFC540Y	540min.	245min.	21min.	22min.				Thickness × 0.5
SPFC590Y	590min.	265min.	18min.	19min.				Thickness × 1.0
SPFC780Y	780min.	365min.	13min.	14min.				Thickness × 3.0
SPFC980Y	980min.	490min.	6min.	7min.				Thickness × 4.0

Remarks : Concerning the applicable thickness of the elongation of SPFC780Y and SPFC980Y, 0.6 mm or over to and excl. 1.0 mm and 1.0 mm or over up to and incl. 2.3 mm shall be respectively shifted to 0.8 mm or over to and excl. 1.0 mm and 1.0 mm or over up to and incl. 2.0 mm.

(2) Automobile Structure Steel with High Strength Dual-phase (780/ 980 N/mm<sup>2</sup> class)

Symbol of Grade	Tension Test				
	Thickness (t) mm	Width (w) mm	Tensile Strength N/mm <sup>2</sup>	Elongation %	Test Piece
SPFC780Y	0.90~2.00	850~1219	780min.	13min.	JIS No.5 Perpendicular to rolling direction
SPFC980Y	0.80~1.80	850~1000	980min.	9min.	

## (3) EN 10268-2006 Cold Rolled Steel Flat Products with High Yield Strength for Cold Forming

Symbol of Grade	chemical composition %								Tension Test <sup>1,2,3,4</sup>					
	C max.	Si max.	Mn max.	P max.	S max.	Al min.	Ti max.	Nb max.	0.2% Proof Stress MPa	Tensile Strength MPa	Elongation		Plastic strain ratio min. r <sub>90</sub>	Strain hardening exponent min. n
											Test Piece	% min.		
HC220P	0.07	0.50	0.70	0.080	0.025	0.015	—	—	220~ 270	320~ 400	EN TYPE 2  Perpen- dicular to rolling direction	32	1.3	0.16
HC220Y	0.01	0.30	0.90	0.080	0.025	0.010	0.12	—	220~ 270	350~ 400		34	1.6	0.18
HC260Y	0.01	0.30	1.60	0.100	0.025	0.010	0.12	—	260~ 320	380~ 440		32	1.4	0.17
HC260LA	0.10	0.50	0.60	0.025	0.025	0.015	0.15	—	260~ 330	350~ 430		26	—	—
HC300LA	0.10	0.50	1.00	0.025	0.025	0.015	0.15	0.09	300~ 380	380~ 480		23	—	—
HC340LA	0.10	0.50	1.10	0.025	0.025	0.015	0.15	0.09	340~ 420	410~ 510		21	—	—
HC380LA	0.10	0.50	1.60	0.025	0.025	0.015	0.15	0.09	380~ 480	440~ 560		19	—	—
HC420LA	0.10	0.50	1.60	0.025	0.025	0.015	0.15	0.09	420~ 520	470~ 590		17	—	—

## Remarks :

1. 1MPa=1 N/mm<sup>2</sup>2. The minimum values for r<sub>90</sub> and n<sub>90</sub> only apply to products of thickness equal to or greater than 0.5 mm.

3. When the thickness is less than or equal to 0.7 mm and greater than 0.5 mm, the minimum value for elongation is reduced by 2 units.

4. For products with thickness over 2 mm the minimum r<sub>90</sub> value is reduced by 0.2.

## (4) SAE J2340 High Strength Automotive Sheet Steel

Symbol of Grade	Chemical Composition <sup>1</sup> %			Tension Test <sup>2</sup>			
	C max.	P max.	S max.	Proof Stress MPa	Tensile Strength MPa	Elongation %	Test Piece
340X	0.13	0.060	0.015	340~440	410min.	22min.	rolling direction
420X	0.13	0.060	0.015	420~520	490min.	18min.	rolling direction

## Remarks :

1. The specified minimum for niobium, titanium, or vanadium is 0.005 %.

2. For thickness less than 2.5 mm, minimum percent elongation is permitted to be 2 % less than the value shown.

(5) CSC Specification

Symbol of Grade	Tension Test					Bend test			
	Tensile Strength N/mm <sup>2</sup>	Proof Stress N/mm <sup>2</sup>	Elongation %			Test Piece	Bend Angle	Radius of Inside surface	Test Piece
			Thickness (t) mm						
			0.55 ≤ t < 1.0	1.0 ≤ t ≤ 2.0	2.0 < t ≤ 2.6				
CSC CF370R	370min.	205min.	33min.	34min.	—	No.5 Perpendicular to rolling direction	180°	Flat on itself	No.3 Perpendicular to rolling direction
CSC CF390R	390min.	235min.	31min.	32min.	—				
CSC CF440R	440min.	255min.	—	—	30min.				

Remark : The bend test shall be carried out on request of the purchaser.

(6) CSC Specification

Symbol of Grade	Tension Test				Bend test			
	Tensile Strength N/mm <sup>2</sup>	Proof Stress N/mm <sup>2</sup>	Elongation %		Test Piece	Bend Angle	Radius of Inside surface	Test Piece
			Thickness (t) mm					
			0.9 ≤ t ≤ 2.0					
CSC CR500LA	570~710	500~620	14min.		EN Type 2 Perpendicular to rolling direction	180°	Thickness×1.0	No.3 Perpendicular to rolling direction

### 7.1.3 CSC High Strength Steel Sheets for Strap

Symbol of Grade	Chemical Composition %					Tension Test			Bend test		
	C	Si	Mn	P	S	Tensile Strength N/mm <sup>2</sup>	Elongation %	Test Piece	Bend Angle	Radius of Inside surface	Test Piece
CSC HS840	0.20 max.	0.50 max.	0.70~1.50	0.030 max.	0.030 max.	840 min.	6.0 min.	JIS No.9A Parallel to rolling direction	90°	Thickness×1.0	JIS No.3 Parallel to rolling direction

### 7.1.4 CSC Steel Sheets for Special Blanking Use

Symbol of Grade	Tension Test		Hardness HRB
	Proof Stress N/mm <sup>2</sup>	Test Piece	
CSC CW205YE	205~245	No.5 parallel to rolling direction	50~56

Remarks :

1. Thickness tolerance as per 1/4 JIS G3141 Class A.
2. Width tolerance as per JIS G3141 Class A.
3. Flatness tolerance as per 1/2 JIS G3141 Class A.

## 7.1.5 CSC Steel Sheets for Fine Blanking Use

Symbol of Grade	Tension Test				Test Piece
	Tensile Strength N/mm <sup>2</sup>	Proof Stress N/mm <sup>2</sup>	Elongation %		
			Thickness (t) mm	%	
CSC CB270TE	270min.	200max.	1.0 ≤ t < 1.6	43min.	No.5 Parallel to rolling direction
			1.6 ≤ t < 2.5	44min.	
			2.5 ≤ t ≤ 3.2	45min.	

Remarks :

1. Thickness tolerance as per 1/4 JIS G3141 Class A.
2. Width tolerance as per JIS G3141 Class A.
3. Flatness tolerance as per 1/2 JIS G3141 Class A.

## 7.1.6 Cold Rolled Medium Carbon Steel, High Carbon Steel, Alloy Steel and Special Steel Strip

(1) JIS G3311-2010 Special Steel Strip

Symbol of Grade	Chemical Composition%									
	C	Si	Mn	P max.	S max.	Cu max.	Ni max.	Cr	Ni+Cr max.	Mo
S35CM	0.32~ 0.38	0.15~ 0.35	0.60~ 0.90	0.030	0.035	0.30	0.20	0.20max.	0.35	—
S45CM	0.42~ 0.48	0.15~ 0.35	0.60~ 0.90	0.030	0.035	0.30	0.20	0.20max.	0.35	—
S50CM	0.47~ 0.53	0.15~ 0.35	0.60~ 0.90	0.030	0.035	0.30	0.20	0.20max.	0.35	—
SK85M	0.80~ 0.90	0.10~ 0.35	0.10~ 0.50	0.030	0.030	0.25	0.25	0.30max.	—	—
SK95M	0.90~ 1.00	0.10~ 0.35	0.10~ 0.50	0.030	0.030	0.25	0.25	0.30max.	—	—
SKS51M	0.75~ 0.85	0.35 max.	0.50 max.	0.030	0.030	0.25	1.30~ 2.00	0.20~ 0.50	—	—
SCM415M	0.13~ 0.18	0.15~ 0.35	0.60~ 0.90	0.030	0.030	0.30	0.25	0.90~ 1.20	—	0.15~ 0.25
SCM435M	0.33~ 0.38	0.15~ 0.35	0.60~ 0.90	0.030	0.030	0.30	0.25	0.90~ 1.20	—	0.15~ 0.30

Remarks : For steel strips and cut-lengths of thicknesses over 4.00 mm or widths 600 mm or over, the thickness tolerance shall be as agreed between the purchaser and the manufacturer.

(2) SAE J403 / J404 (Medium Carbon Steel, High Carbon Steel and Alloy Steel)

Symbol of Grade	Chemical Composition %						
	C	Si	Mn	P	S	Cr	Mo
1050	0.48~0.55	—	0.60~0.90	0.030max.	0.050max.	—	—
1055	0.50~0.60		0.60~0.90				
1060	0.55~0.65		0.60~0.90				
1065	0.60~0.70		0.60~0.90				
1070	0.65~0.75		0.60~0.90				
1552	0.47~0.55	—	1.20~1.50	0.030max.	0.050max.	—	—
4130	0.28~0.33	0.15~0.35	0.40~0.60	0.030max.	0.040max.	0.80~1.10	0.15~0.25
4135	0.33~0.38	0.15~0.35	0.70~0.90	0.030max.	0.040max.	0.80~1.10	0.15~0.25

## (3) ASTM A684-2008 (High Carbon Steel)

Symbol of Grade	Chemical Composition %				
	C	Si	Mn	P	S
1050	0.48~0.55	0.15~0.30	0.60~0.90	0.030max.	0.035max.
1065	0.60~0.70	0.15~0.30	0.60~0.90	0.030max.	0.035max.
1070	0.65~0.75	0.15~0.30	0.60~0.90	0.030max.	0.035max.

## 7.1.7 CSC Steel Sheets for Slide Rail Use

Symbol of Grade	Tension Test		Bend test			Hardness HRB
	Proof Stress N/mm <sup>2</sup>	Test Piece	Bend Angle	Radius of Inside surface	Test Piece	
CSC SL250Y	250~330	No.5 Perpendicular to rolling direction	180 <sup>o</sup>	Thickness × 1.0	No.3 Perpendicular to rolling direction	65~80
CSC SL330Y	330~410					72~82
CSC SL420Y	420min.					—

## Remarks :

1. Thickness tolerance as per 1/2 JIS G3141 Class A.
2. Width tolerance as per JIS G3141 Class A.
3. Flatness tolerance as per 1/2 JIS G3141 Class A.
4. For SL420Y, thickness tolerance as per 1/2 JIS G3135.

## 7.1.8 Decarburized Steel Sheets and Strip for Porcelain Enameling

Symbol of Grade	Chemical Composition <sup>(1)</sup> %				Tension Test <sup>(2)</sup>		Test Piece
	C	Mn	P	S	Elongation %		
					Thickness(t) mm	%	
SPP	0.008 max.	0.50 max.	0.04 max.	0.04 max.	0.40 ≤ t < 0.60	36min.	No.5 Parallel to rolling direction
					0.60 ≤ t < 1.00	38min.	
					1.00 ≤ t < 1.60	39min.	
					1.60 ≤ t < 2.00	40min.	

## Remarks :

1. Such elements as Ti, Nb, Zr, V and B may be added. In this case, the content of the elements added shall be reported.
2. For steel sheets and strip under 0.60mm in thickness, the tension test shall normally be omitted when not requested by the purchaser.

### 7.1.9 CSC Low-carbon High Manganese Wear-resisting Steel

Symbol of Grade	Thickness (t)mm	Width (w)mm	Hardness HRB
CSC CC1513	$1.61 \leq t \leq 1.97$	$850 \leq w \leq 1250$	65~75

Remarks :

1. Thickness tolerance as per ASTM A568.
2. Flatness tolerance as per ASTM A568.

### 7.1.10 CSC High Strength Manganese-boron Steel

Symbol of Grade	Chemical Composition %							Tension Test	
	C	Si	Mn	P	S	Al	B	Elongation %	Test piece
CSC CC15B22	0.19~ 0.25	0.15~ 0.25	1.05~ 1.35	0.020 max.	0.010 max.	0.075 max.	0.0005~ 0.0045	26 min.	JIS No.5 Parallel to rolling direction

Remark : Thickness tolerance as per 1/2 JIS G3141 Class A.

### 7.1.11 CSC Steel Sheets for Relay Use

Symbol of Grade	Thickness (t) mm	Width (w) mm	Hardness HRB	Tension Test	
				Elongation %	Test piece
CSC CM-1	$0.40 \leq t \leq 3.20$	$850 \leq w \leq 1250$	35min.	37min.	JIS No.5 Parallel to rolling direction

Remarks :

1. Thickness tolerance as per 1/2 JIS G3141 Class A.
2. Thickness of 2.01 mm or more of the steel sheet are subject to the coil breaks.

### 7.1.12 CSC Low-carbon Bearing Retainer Steel

Symbol of Grade	Chemical Composition %				Tension Test			Hardness HRB
	C	Mn	P	S	Thickness (t) mm	Proof Stress N/mm <sup>2</sup>	Test Piece	
CSC CF170YF	0.15 max.	0.60 max.	0.100 max.	0.050 max.	$0.50 \leq t \leq 0.80$	170~230	No.5 Parallel to rolling direction	45~55

Remark : Thickness tolerance as per 1/4 JIS G3141 Class A.

## 7.2 Tolerances

### 7.2.1 Thickness Tolerances

#### 7.2.1.1 JIS G3141 Thickness Tolerances

unit : mm

Tolerance Thickness (t)	Width (w)				
	w < 630	630 ≤ w < 1000	1000 ≤ w < 1250	1250 ≤ w < 1630	w ≥ 1630
t < 0.25	±0.03	±0.03	±0.03	—	—
0.25 ≤ t < 0.40	±0.04	±0.04	±0.04	—	—
0.40 ≤ t < 0.60	±0.05	±0.05	±0.05	±0.06	—
0.60 ≤ t < 0.80	±0.06	±0.06	±0.06	±0.06	±0.07
0.80 ≤ t < 1.00	±0.06	±0.06	±0.07	±0.08	±0.09
1.00 ≤ t < 1.25	±0.07	±0.07	±0.08	±0.09	±0.11
1.25 ≤ t < 1.60	±0.08	±0.09	±0.10	±0.11	±0.13
1.60 ≤ t < 2.00	±0.10	±0.11	±0.12	±0.13	±0.15
2.00 ≤ t < 2.50	±0.12	±0.13	±0.14	±0.15	±0.17
2.50 ≤ t < 3.15	±0.14	±0.15	±0.16	±0.17	±0.20
3.15 ≤ t	±0.16	±0.17	±0.19	±0.20	—

Remark : Thickness shall be measured at any point 15 mm or more apart from both edges.

#### 7.2.1.2 JIS G3135 Thickness Tolerances

unit : mm

Applicable division according to tensile strength	Width (w)					
	Thickness (t)	w < 630	630 ≤ w < 1000	1000 ≤ w < 1250	1250 ≤ w < 1600	1600 ≤ w
Steel sheets of under 780 N/mm <sup>2</sup> in specification lower limit of tensile strength	0.60 ≤ t < 0.80	±0.06	±0.06	±0.06	±0.07	±0.08
	0.80 ≤ t < 1.00	±0.07	±0.07	±0.08	±0.09	±0.10
	1.00 ≤ t < 1.25	±0.08	±0.08	±0.09	±0.10	±0.12
	1.25 ≤ t < 1.60	±0.09	±0.10	±0.11	±0.12	±0.14
	1.60 ≤ t < 2.00	±0.10	±0.11	±0.12	±0.14	±0.16
	2.00 ≤ t ≤ 2.30	±0.12	±0.13	±0.14	±0.16	±0.18
Steel sheets of 780 N/mm <sup>2</sup> min. in specification lower limit of tensile strength	0.80 ≤ t < 1.00	±0.09			±0.10	—
	1.00 ≤ t < 1.25	±0.10			±0.12	—
	1.25 ≤ t < 1.60	±0.12			±0.15	—
	1.60 ≤ t ≤ 2.00	±0.14			±0.16	—

Remarks : 1. The measuring position of thickness shall be an arbitrary point 25 mm min. apart from the edge for a mill edge and an arbitrary point 15 mm min. apart from the edge for a cut edge.

2. This table shall not be applied to the abnormal parts at both ends of steel strip in coil.

## 7.2.1.3 CSC CF370R/390R/440R Thickness Tolerances

unit : mm

Thickness (t) \ Width (w)	$850 \leq w < 1000$	$1000 \leq w < 1250$	$1250 \leq w$
$0.55 \leq t < 0.60$	$\pm 0.02$	$\pm 0.02$	$\pm 0.03$
$0.60 \leq t < 0.80$	$\pm 0.03$	$\pm 0.03$	$\pm 0.03$
$0.80 \leq t < 1.00$	$\pm 0.03$	$\pm 0.04$	$\pm 0.04$
$1.00 \leq t < 1.25$	$\pm 0.04$	$\pm 0.04$	$\pm 0.05$
$1.25 \leq t < 1.60$	$\pm 0.05$	$\pm 0.05$	$\pm 0.06$
$1.60 \leq t \leq 2.00$	$\pm 0.05$	$\pm 0.06$	$\pm 0.07$

Remark : Thickness shall be measured at any point 15 mm or more apart from both edges.

## 7.2.1.4 ASTM A568 Thickness Tolerances ( All Designations ) (Specified Nominal Thickness Tolerances)

unit : in. ( mm)

Thickness (t) \ Width (w)	$15 (381) < w \leq 72 (1829)$
$0.014 (0.36) \leq t \leq 0.019 (0.48)$	$\pm 0.0010 (0.025)$
$0.019 (0.48) < t \leq 0.039 (0.99)$	$\pm 0.0015 (0.038)$
$0.039 (0.99) < t \leq 0.057 (1.45)$	$\pm 0.0020 (0.050)$
$0.057 (1.45) < t \leq 0.071 (1.80)$	$\pm 0.0025 (0.063)$
$0.071 (1.80) < t \leq 0.098 (2.49)$	$\pm 0.0025 (0.063)$
$0.098 (2.49) < t \leq 0.142 (3.60)$	$\pm 0.0030 (0.076)$

Remark : Thickness shall be measured at any point 1 inch (25.4 mm) or more apart from both edges.

## 7.2.1.5 ASTM A568M Thickness Tolerances ( All Designations ) (Specified Nominal Thickness Tolerances) unit : mm

Thickness (t) \ Width (w)	$780 \leq w \leq 1829$
$0.20 \leq t \leq 0.40$	$\pm 0.025$
$0.40 < t \leq 1.00$	$\pm 0.040$
$1.00 < t \leq 1.20$	$\pm 0.050$
$1.20 < t \leq 2.50$	$\pm 0.060$
$2.50 < t \leq 3.00$	$\pm 0.075$

Remark : Thickness shall be measured at any point 25 mm or more apart from both edges.

7.2.1.6 EN 10131 EN 10131 Thickness Tolerances (Minimum Yield Strength  $Re < 260$  MPa)

unit : mm

Tolerance Thickness (t)	Width (w)	$w \leq 1200$	$1200 < w \leq 1500$	$1500 < w$
		$0.35 \leq t \leq 0.40$	$\pm 0.03$	$\pm 0.04$
$0.40 < t \leq 0.60$	$\pm 0.03$	$\pm 0.04$	$\pm 0.05$	
$0.60 < t \leq 0.80$	$\pm 0.04$	$\pm 0.05$	$\pm 0.06$	
$0.80 < t \leq 1.00$	$\pm 0.05$	$\pm 0.06$	$\pm 0.07$	
$1.00 < t \leq 1.20$	$\pm 0.06$	$\pm 0.07$	$\pm 0.08$	
$1.20 < t \leq 1.60$	$\pm 0.08$	$\pm 0.09$	$\pm 0.10$	
$1.60 < t \leq 2.00$	$\pm 0.10$	$\pm 0.11$	$\pm 0.12$	
$2.00 < t \leq 2.50$	$\pm 0.12$	$\pm 0.13$	$\pm 0.14$	
$2.50 < t \leq 3.00$	$\pm 0.15$	$\pm 0.15$	$\pm 0.16$	

7.2.1.7 EN 10131 Thickness Tolerances (Minimum Yield Strength  $260 \leq Re < 340$  MPa )

unit : mm

Tolerance Thickness (t)	Width (w)	$w \leq 1200$	$1200 < w \leq 1500$	$1500 < w$
		$0.35 \leq t \leq 0.40$	$\pm 0.04$	$\pm 0.05$
$0.40 < t \leq 0.60$	$\pm 0.04$	$\pm 0.05$	$\pm 0.06$	
$0.60 < t \leq 0.80$	$\pm 0.05$	$\pm 0.06$	$\pm 0.07$	
$0.80 < t \leq 1.00$	$\pm 0.06$	$\pm 0.07$	$\pm 0.08$	
$1.00 < t \leq 1.20$	$\pm 0.07$	$\pm 0.08$	$\pm 0.10$	
$1.20 < t \leq 1.60$	$\pm 0.09$	$\pm 0.11$	$\pm 0.12$	
$1.60 < t \leq 2.00$	$\pm 0.12$	$\pm 0.13$	$\pm 0.14$	
$2.00 < t \leq 2.50$	$\pm 0.14$	$\pm 0.15$	$\pm 0.16$	
$2.50 < t \leq 3.00$	$\pm 0.17$	$\pm 0.18$	$\pm 0.18$	

7.2.1.8 EN 10131 Thickness Tolerances (Minimum Yield Strength  $340 \leq Re \leq 420$  MPa)

unit : mm

Tolerance Thickness (t)	Width (w)	$w \leq 1200$	$1200 < w \leq 1500$	$1500 < w$
		$0.35 \leq t \leq 0.40$	$\pm 0.04$	$\pm 0.05$
$0.40 < t \leq 0.60$	$\pm 0.04$	$\pm 0.05$	$\pm 0.06$	
$0.60 < t \leq 0.80$	$\pm 0.05$	$\pm 0.06$	$\pm 0.07$	
$0.80 < t \leq 1.00$	$\pm 0.06$	$\pm 0.07$	$\pm 0.08$	
$1.00 < t \leq 1.20$	$\pm 0.07$	$\pm 0.08$	$\pm 0.10$	
$1.20 < t \leq 1.60$	$\pm 0.09$	$\pm 0.11$	$\pm 0.12$	
$1.60 < t \leq 2.00$	$\pm 0.12$	$\pm 0.13$	$\pm 0.14$	
$2.00 < t \leq 2.50$	$\pm 0.14$	$\pm 0.15$	$\pm 0.16$	
$2.50 < t \leq 3.00$	$\pm 0.17$	$\pm 0.18$	$\pm 0.18$	

## 7.2.2 Width Tolerances

### 7.2.2.1 JIS G3141 Width Tolerances

unit : mm

Width (w)	Class A		Class B	
	Upper	Lower	Upper	Lower
$w < 1250$	7	0	3	0
$w \geq 1250$	10	0	4	0

Remark : Class B generally applies to the re-cutting or precise cutting practice. Unless specified by the customer, class A is to be applied.

### 7.2.2.2 Width Tolerances of JIS G3135 and CSC CF370R/390R/440R

unit : mm

Width (w)	Tolerances	
	Upper	Lower
$w < 1250$	7	0
$w \geq 1250$	10	0

### 7.2.2.3 ASTM A568 Width Tolerances ( All Designations ) (Specified Nominal Thickness Tolerances)

unit : in. ( mm )

Width (w)	Tolerances	
	Upper	Lower
$30 (762) < w \leq 48 (1219)$	3/16 (4.7)	0
$48 (1219) < w \leq 60 (1524)$	1/4 (6.3)	0
$60 (1524) < w \leq 80 (2032)$	5/16 (7.9)	0

### 7.2.2.4 ASTM A568M Width Tolerances(All Designations)(Specified Nominal Thickness Tolerances)

unit : mm

Width (w)	Tolerances	
	Upper	Lower
$850 < w \leq 1200$	5	0
$1200 < w \leq 1500$	6	0
$1500 < w \leq 1800$	8	0
$1800 < w$	10	0

### 7.2.2.5 EN 10131 Width Tolerances

unit : mm

Width (w)	Tolerances	
	Upper	Lower
$w \leq 1200$	4	0
$1200 < w \leq 1500$	5	0
$1500 < w$	6	0

## 7.2.3 Flatness Tolerances

### 7.2.3.1 JIS G3141 Flatness Tolerances

unit : mm

Flatness (max.) Width (w)	Classification	Class A			Class B		
		Bow Wave	Edge Wave	Center Buckle	Bow Wave	Edge Wave	Center Buckle
$w < 1000$		12	8	6	2	2	2
$1000 \leq w < 1250$		15	9	8	3	2	2
$1250 \leq w < 1600$		15	11	8	4	3	2
$1600 \leq w$		20	13	9	5	4	2

Remarks : 1. Class B generally applies to the steel sheets of stretcher-leveled steel sheet.  
2. Class A applies to the normally refined steel sheets.

### 7.2.3.2 JIS G3135 Flatness Tolerances

unit : mm

Flatness (max.) Width (w)	Classification	Bow Wave			Edge Wave			Center Buckle		
		1	2	3	1	2	3	1	2	3
$w < 1000$		12	16	18	8	11	12	6	8	9
$1000 \leq w < 1250$		15	19	21	10	12	13	8	10	11
$1250 \leq w < 1600$		15	19	21	12	14	15	9	11	12
$1600 \leq w$		20	-	-	14	-	-	10	-	-

Remarks : 1. Grade 1 to 3 shall respectively be applied to the steel sheet of which the lower limit specification value of tensile strength is under 780 N/mm<sup>2</sup>, 780 N/mm<sup>2</sup> and 980 N/mm<sup>2</sup>.  
2. The value of flatness shall, as a rule, be measured by placing the steel sheet on a surface plate. It shall be obtained by subtracting nominal thickness of steel sheet from the maximum value of strain and be applied to the upper side surface of steel sheet.

### 7.2.3.3 Flatness Tolerances for CSC CF370R/390R/440R

The flatness tolerances for 0.79mm and under in thickness shall conform to table A of JIS G3141, and for 0.80mm and over in thickness shall conform to 1/2 of table A of JIS G3141.

**7.2.3.4 ASTM A568 Flatness Tolerances(All Designations)(Specified Nominal Thickness Tolerances)** unit : in. (mm)

Thickness(t)	Width (w)	Specified Yield Point	
		Under 45ksi (Under 310 MPa)	45 to 50 ksi (310 to 345 MPa)
$t \leq 0.044$ (1.12)	$w \leq 36$ (914)	3/8 ( 9.5)max.	3/4 ( 19.1)max.
	$36$ (914) < $w \leq 60$ (1524)	5/8 (15.9)max.	1 1/8 (28.6)max.
	$60$ (1524) < $w$	7/8 (22.2)max.	1 1/2 (38.1)max.
$0.044$ (1.12) < $t$	$w \leq 36$ (914)	1/4 ( 6.4)max.	3/4 ( 19.1)max.
	$36$ (914) < $w \leq 60$ (1524)	3/8 ( 9.5)max.	3/4 ( 19.1)max.
	$60$ (1524) < $w \leq 72$ (1829)	5/8 (15.9)max.	1 1/8 (28.6)max.

Remarks : Tolerances for high-strength, low-alloy steel with specified minimum yield point in excess of 50 ksi are subject to negotiation.

**7.2.3.5 ASTM A568M Flatness Tolerances(All Designations)(Specified Nominal Thickness Tolerances)** unit : mm

Thickness(t)	Width (w)	Specified Yield Point	
		Under 310 MPa	310 to 345 MPa
$t \leq 1.0$	$w \leq 900$	10max.	20max.
	$900 < w \leq 1500$	15max.	30max.
	$1500 < w$	20max.	40max.
$1.0 < t$	$w \leq 900$	8max.	20max.
	$900 < w \leq 1500$	10max.	20max.
	$1500 < w \leq 1800$	15max.	30max.

Remarks : Tolerances for high-strength, low-alloy steel with specified minimum yield point in excess of 340 MPa are subject to negotiation.

## 7.2.4 Camber Tolerances

### 7.2.4.1 JIS G3141 Camber Tolerances

unit : mm

Width (w)	Tolerance (max.)
$630 \leq w$	2 (Any portion of 2000 in length)

### 7.2.4.2 Camber Tolerances of JIS G3135 and CSC CF370R/390R/440R

unit : mm

Lower limit specification value of tensile strength	Width (w)	Tolerances (max.)
Under $780 \text{ N/mm}^2$	$w \geq 630$	2 per an arbitrary length of 2000
$780 \text{ N/mm}^2$ or over	$w \geq 630$	3 per an arbitrary length of 2000

### 7.2.4.3 ASTM A568 Camber Tolerances

Production	Tolerance (max.)
Coils	1/4 inch (6.35mm) in any 8 ft ( 2438 mm)


### 7.2.4.4 ASTM A568M (Metric) Camber Tolerances

unit : mm

Production	Tolerance (max.)
Coils	5.0 in any 2000

### 7.3 Classification of Quality

Classification	Quality	Common Specification	Typical Applications
For Forming Fabrication	Commercial Quality (CQ)	JIS G3141 SPCC JFS A2001 JSC270C ASTM A1008 CS EN10130 DC01 CSC CB270TE	Furniture Refrigerator Case, Piping, Steel Drum, Tool Box, Computer Case, Cabinet Lock, Electronic Parts, Wheel Rim & Cap etc.
	Drawing Quality (DQ)	JIS G3141 SPCD JFS A2001 JSC270D ASTM A1008 DS EN 10130 DC03	Motor Housing Fender, Chassis, Lamp Shell, Door Inner, & Outer for Automobile, Roaster Oven, etc.
	Deep Drawing Quality (DDQ)	JIS G3141 SPCE/SPCF JFS A2001 JSC270E ASTM A1008 DDS EN 10130 DC04	Fuel Tank, Oil Can, Fender, Bumper, Trunk Lid Inner, Door Inner for Automobile, Front Lamp Set, Lighting Fixture, etc.
	Extra Deep Drawing Quality (EDDQ)	JIS G3141 SPCG JFS A2001 JSC270F ASTM A1008 EDDS EN 10130 DC05	Oil Can, Fuel Tank for Automobile, Lid inner & Door inner for Automobile, etc.
For Structural Use	Structural Quality (SS)	ASTM A1008 SS Grade XX	Frame, Automobile Body, Roofing Deck, etc
	High Strength Sheet With Improved Formability for Automobile Quality	JIS G3135 SPFCXXX JFS A2001 JSCXXX EN 10268 HCXXX CSC CF370R/390R/440R	Fender Bumper, Luggage Carrier, Automobile Frame, Bonnet and Trunk, etc.
	Bicycle parts	CSC CC1513	Chain Wheel for Bicycle
For Hardware, Tool Use	Special Steel Strip	JIS G3311 ASTM A684 SAE J404	Chain Plate, Hand Tool, Saw Plate, Golf Club

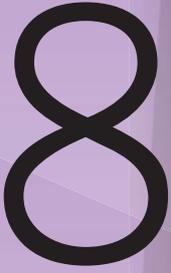

## 8.1 Unit mass

Product Type	Minimum Unit mass
CR Coil (Carbon Steel)	3 t / Coil
CR Coil (High Strength Low Alloy Steel)	3 t / Coil

## 8.2 Available Sizes

unit : mm

Product Type	Thickness	Width	Coil Inside Diameter
CR Coil (Carbon Steel)	0.20~0.29	850~1000	508 or 610
	0.30~0.34	850~1100	
	0.35~0.40	850~1219	
	0.41~0.49	780~1250	
	0.50~0.59	780~1410	
	0.60~0.69	780~1630	
	0.70~0.79	780~1776	
	0.80~1.60	780~1830	
	1.61~2.00	780~1676	
	2.01~3.20	780~1250	
CR Coil (High Strength Low Alloy Steel)	0.40~2.00	850~1520	
CR Coil (Special Steel Strip)	0.40~2.50	850~1000	


Remark : Above as a reference only.

## 9.1 Marking for cold rolled steel



Making Item	1	2	3	4	5	6	7	8	9	10	11
	CSC logo	CSC name	Product name	Specification	Size	Identification	Net mass	Gross mass	Quality type	Rough code	Heat no

## 9.2 Packing for cold rolled steel

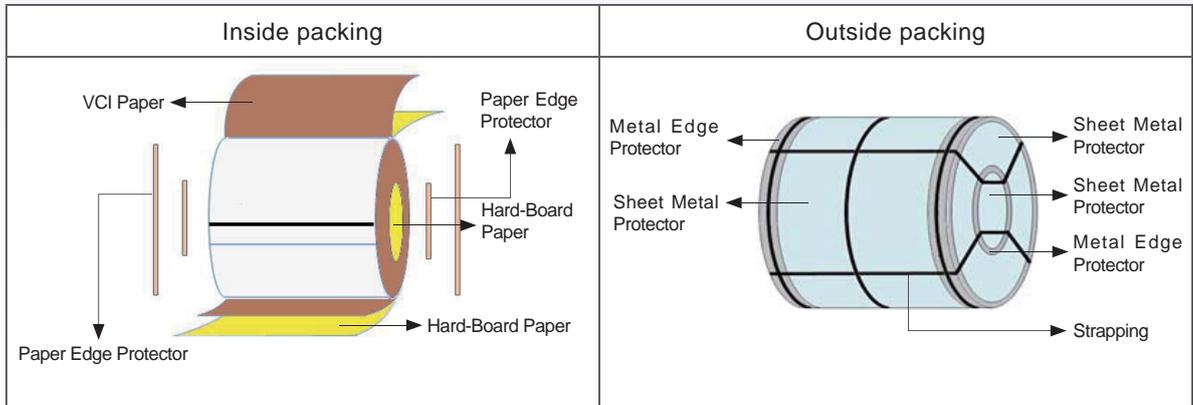

Material	Paper Pipe	VCI Paper	Hard-Board Paper			Paper Edge Protector		Sheet Metal Protector			Metal Edge Protector	
			circumferential surface	side wall	inner surface	outside diameter	inside diameter	circumferential surface	side wall	inner surface	outside diameter	inside diameter
Cold Rolled Coil		V	V			V	V	V	V	V	V	V
Non-Oiled Cold Rolled Coil		V	V		V	V	V	V	V	V	V	V
Thin Cold Rolled Coil	V	V	V			V	V	V	V	V	V	V
Non-Oiled Thin Cold rolled Coil	V	V	V		V	V	V	V	V	V	V	V

# 10



## 10.1 Rust Prevention

---

If antirust treatment is not properly performed for the cold-rolled steel coils and sheets, it will be easy to rust the steel surface. Therefore, the coils have to be spread with proper rust preventive oil, and the coils are packed completely to protect them before shipping. However, the steel sheets and coils are easy to rust owing to the environmental factors during their storage and use. Especially the condensation problems are easy to occur when the coil storage is in an environment of high humidity and high/low temperature with rapid changes. Therefore, it should particularly pay attention to the prevention of condensation and drain water in advance. Besides, since the dust or acidic substance in the atmosphere are also easy to rust the surface of steel coils or sheets, such problems in the storage or processing must be eliminated for keeping good surface quality.

## 10.2 Stretcher strain and Aging

---

There are solid solution Carbon and Nitrogen in the low carbon steels. If they are not treated properly, the stretcher strain marks will be occurred in the process. Therefore, the temper rolling process will be carried out appropriately on these products to eliminate the extension of yield point. However, the extension of yield point may appear again with the longer period of storage as we called the aging problem. Aging is mainly related to solid solution Carbon \ storing temperature and time. The “first in, first out (FIFO)” management to use these grades of steel is recommended as soon as possible in order to avoid the aging problems

## 10.3 Painting

---

The painting is one of the common ways to apply for further protecting the cold-rolled products, or enhancing their beauty and function. Not only the paint itself but also the painting pre-treatment is important factor to influence the coating performance. The main factors resulting in poor painting are:

- (a) Insufficient clean: The residual oil and contaminant are often seen on the steel surfaces. These foreign matters may cause the paint to be unable to bond to the substrate surfaces, and may result in declining to fail the adhesion of film. It is better to understand the rust preventive oil, lubricants and other characteristics, proper choosing the way of cleaning and cleaning agents, paying more attention to storage conditions and painting operation environment for helping to improve the insufficient clean.
- (b) Unsuitable chemical treatment: If the passivation film of chemical treatment is not sufficient or uneven, once outside corrosion factors are contacted with metal, the reactive metal is very easy to oxidize. Then oxide will thoroughly destroy the adhesion of primer paint to the steel surface. Moreover, if there are loose passivation films and coarse crystals or the residue contamination on the chemical treatment liquid, it will also cause the deficiency of the film adhesion. It is better to understand the reaction properties of the chemical treatment liquid, paying more attention on the differences between different cold-rolled steel sheet surfaces, properly adjusting the treatment

liquid concentration, temperature and time, as well as emphasizing on the clean of the treated surface.

- (c) Improper paint : The environment and the end-use of products should be considered in the selection of paint, and the appropriate painting procedure should be adopted to ensure that the treated substrate surfaces are sufficiently wetted, are compatible with the paint, and have the ability to resist the environmental corrosion factors.

## 10.4 Electroplating

---

Electroplating is covering the cold-rolled steel sheets with a layer of metal or alloy by the principle of electrolysis, and the finishing products will have decorative metallic color and property. After electroplated, the appearance of the electroplated object is related to the current density. In the operational current density range, when the current density is smaller, the electroplated object will be more beautiful. Oppositely, there will be some uneven shapes. Generally, the electroplating bath is acidic that can dissolve the coating layer of Cathode. When the current density is too small, as a result of the dissolution of the acidic bath, the metal of coating layer will show the appearance of loose and matt. The contaminated water generated by electroplating process is an important source of water pollution, which is needed to concentrate on sewage treatment. The common electroplating is zinc-coated \ copper-coated \ nickel-coated \ chrome-coated. The main factors resulting in poor electroplating are:

- (a) Uneven coated layer: To obtain a uniform coated method is the well composition of coating bath. The reasonable operation makes the surface activity to be uniform. The reasonable hanging of the coated pieces makes the best current to be distributed uniformly. The current distribution can be improved by the distance and height between the anode and cathode, and by adding to auxiliary electrode \ transmission device \ insulation barrier etc.
- (b) Coated layer with slag: Since it is due to impurity contamination, and impurity accumulation of long operation, it must always purify the coating bath. The main methods are : To use the filter material to remove solid impurities, to use activated carbon to remove organic matter, and to remove the metallic impurities by the electrolysis. Furthermore, the impurities can be removed by using the chemical methods of replacement \ precipitation \ pH adjustment and others.
- (c) Coated layer with poor adhesion: It is due to the poor surface pre-treatment and oil contamination that the coated layer is unable to combine with the substrate. Therefore, it must execute the proper degreasing clean sufficiently.

## 10.5 Welding

---

- (a) To compare with galvanized steel sheets, there are higher resistance values on cold-rolled steel sheets that only need a small welding current or shorter welding time to obtain sufficient resistance welding heat.
- (b) Because the cold-rolled steel does not have the galvanized layer, there will be no phenomenon of the foreign

matter contaminated with electrodes in the welding process. The electrode durability of the cold-rolled steel sheets is higher than that of the galvanized steel sheets. Therefore, the electrode must be replaced or polished during welding if necessary.

(c) Although the cold-rolled steel sheets do not have the interference of the galvanized layer, it still needs to consider the correct welding parameters (welding time and welding current) that can obtain the correct welding strength and life of electrode tip.

(d) The resistance welding process as an example, if you want to weld the cold-rolled steel sheets, please refer to the following table of suggested welding parameters to ensure stable welding quality.

Suggested welding parameter table

Thickness of Steel (mm)	Electrode force (kgf)	Electrode Face Diameter (mm)	Holding time before welding (cyc)	Welding time (cyc)	Welding Current (kA)	Holding time after welding (cyc)
0.30~0.49	170	5	> 30	7	Expulsion of welding current-0.4	2
0.50~0.69	180	5	> 30	8	Expulsion of welding current-0.4	2
0.70~0.89	210	6	> 30	9	Expulsion of welding current-0.4	2
0.90~1.09	230	6	> 30	10	Expulsion of welding current-0.4	3
1.10~1.29	250	6	> 30	12	Expulsion of welding current-0.4	3
1.30~1.49	270	6	> 30	14	Expulsion of welding current-0.4	3
1.50~1.69	300	6	> 30	16	Expulsion of welding current-0.4	4
1.70~1.89	340	6	> 30	18	Expulsion of welding current-0.4	4
1.90~2.09	380	6 or 8	> 30	20	Expulsion of welding current-0.4	4
2.10~2.29	420	6 or 8	> 30	24	Expulsion of welding current-0.4	6
2.30~2.49	450	8	> 30	26	Expulsion of welding current-0.4	6

# 11

## CONVERSION TABLES

Length	ft	inch	mm	m
	1	12	304.8	0.3048
	0.08333	1	25.4	0.0254
	0.003281	0.03937	1	0.001

Mass	1kg = 2.20462 lb
------	------------------

Force	1kgf = 9.80665 N
-------	------------------

Stress	ksi (= 1000psi)	psi	kgf/mm <sup>2</sup>	N/mm <sup>2</sup> (=MPa)
	1	1000	0.70307	6.89476
	0.001	1	$7.0307 \times 10^{-4}$	$6.89476 \times 10^{-3}$
	1.42233	1422.33	1	9.80665
	0.145038	145.038	0.101972	1

Absorbed Energy	ft-lbf	kgf-m	N-m (=Joule)
	1	0.138255	1.35582
	7.23301	1	9.80665
	0.737562	0.101972	1

**Conversion Table from HR30T to HRB**

HR30T	Converted HRB						
35.0	28.1	47.0	46.0	59.0	63.9	71.0	81.9
36.0	29.6	48.0	47.5	60.0	65.4	72.0	83.4
37.0	31.1	49.0	49.0	61.0	66.9	73.0	84.9
38.0	32.5	50.0	50.5	62.0	68.4	74.0	86.4
39.0	34.0	51.0	52.0	63.0	69.9	75.0	87.9
40.0	35.5	52.0	53.5	64.0	71.4	76.0	89.4
41.0	37.0	53.0	55.0	65.0	72.9	77.0	90.8
42.0	38.5	54.0	56.5	66.0	74.4	78.0	92.3
43.0	40.0	55.0	58.0	67.0	75.9	79.0	93.8
44.0	41.5	56.0	59.5	68.0	77.4	80.0	95.3
45.0	43.0	57.0	60.9	69.0	78.9	81.0	96.8
46.0	44.5	58.0	62.4	70.0	80.4	82.0	98.3

Note : This conversion table shall be in accordance with ASTM E140. Hardness not in the table of ASTM is obtained by interpolation.

**Conversion Table from HR15T to HRB**

HR15T	Converted HRB						
70.0	28.8	76.0	47.3	82.0	65.8	88.0	84.3
70.5	30.3	76.5	48.8	82.5	67.3	88.5	85.8
71.0	31.9	77.0	50.4	83.0	68.8	89.0	87.3
71.5	33.4	77.5	51.9	83.5	70.4	89.5	88.9
72.0	35.0	78.0	53.4	84.0	71.9	90.0	90.4
72.5	36.5	78.5	55.4	84.5	73.5	90.5	92.0
73.0	38.0	79.0	56.5	85.0	75.0	91.0	93.5
73.5	39.6	79.5	58.1	85.5	76.6	91.5	95.0
74.0	41.1	80.0	59.6	86.0	78.1	92.0	96.6
74.5	42.7	80.5	61.1	86.5	79.6	92.5	98.1
75.0	44.2	81.0	62.7	87.0	81.2	93.0	99.7
75.5	45.7	81.5	64.2	87.5	82.7		

Note : This conversion table shall be in accordance with ASTM E140. Hardness not in the table of ASTM is obtained by interpolation.

Conversion Table from HV to HRB

HV	Converted HRB	HV	Converted HRB	HV	Converted HRB	HV	Converted HRB
85	41.0	145	76.6	210	93.4	330	—
90	48.0	150	78.7	220	95.0	340	( 108.0)
95	52.0	155	79.9	230	96.7	350	—
100	56.2	160	81.7	240	98.1	360	( 109.0)
105	59.4	165	83.1	250	99.5	370	—
110	62.3	170	85.0	260	( 101.0)	380	( 110.0)
115	65.0	175	86.1	270	( 102.0)		
120	66.7	180	87.1	280	( 103.5)		
125	69.5	185	88.8	290	( 104.5)		
130	71.2	190	89.5	300	( 105.5)		
135	73.2	195	90.7	310	—		
140	75.0	200	91.5	320	( 107.0)		

Note : 1. This conversion table shall be in accordance with ASTM E140. Hardness not in the table of ASTM is obtained by interpolation.

2. The value in parentheses is out of the scope of HRB and for reference. It may be reported as the round number.

# 12

## Mild Steel

Classification	JIS G3141	JFS A2001	ASTM A1008	SAE J2329	EN 10130
CQ	SPCC	JSC270C	CS	Gr.1	DC01
DQ	SPCD	JSC270D	DS	Gr.2	DC03
DDQ	SPCE	JSC270E	DDS	Gr.3	DC04
EDDQ	SPCF	JSC270F	EDDS	Gr.4	DC05
SEDDQ	SPCG	JSC270G	—	Gr.5	DC06

## Structural Steel-Commercial Type/Deep-drawing Type/Bake-hardening Type

Classification	JIS G3135	JFS A2001	ASTM A1008 (SS)	SAE J1392	SAE J2340	EN 10268
Commercial Type	—	—	Gr.25	—	—	—
	—	JSC340W	Gr.30	—	—	—
	SPFC370	JSC370W	Gr.33	035CL	—	HC220P
	SPFC390	JSC390W	Gr.40	040CL	300S	—
	SPFC440	JSC440W	—	045CL		HC260P
Deep-drawing Type	—	JSC340P	—	—	180A	—
	—	JSC370P	—	—	210A	HC220Y
	—	JSC390P	—	—	250A	—
	—	JSC440P	—	—	280A	HC260Y
Bake-hardening Type	—	JSC270H	—	—	—	—
	—	JSC340H	—	—	180B	HC180B
	—		—	—	210B	HC220B
	—	—	—	—	250B	HC260B
	—	—	—	—	280B	HC300B

Structural Steel –High Yeild Ratio Type/ Low Yeild Ratio Type

Classification	JIS G3135	JFS A2001	ASTM A1008 (HSLAS)	SAE J1392	SAE J2340	EN 10268
High Yeild Ratio Type	—	—	Gr.45	045XL	300X	HC300LA
	—	JSC440R	Gr.50	050XL	340X	HC340LA
	—	—	Gr.55	—	380X	HC380LA
	—	—	Gr.60	060XL	420X	HC420LA
	—	JSC590R	Gr.65	—	—	—
	—	—	Gr.70	070XL	490X/R	—
	—	—	Gr.80	080XL	550X/R	—
	—	—	—	—	700R	—
	—	—	—	—	830R	—
	—	—	—	—	600DH	—
	—	—	—	—	700DH	—
Low Yeild Ratio Type	—	—	—	—	500DL	—
	—	—	—	—	600DL1	—
	SPFC590Y	JSC590Y	—	—	600DL2	—
	SPFC780Y	JSC780Y	—	—	800DL	—
	SPFC980Y	JSC980Y	—	—	950DL	—
	—	—	—	—	1000DL	—
	—	JSC1180Y	—	—	—	—

Note : The grades of these specifacaitons are simllilar, not the same in the table above

# 13

## ORDERING INFORMATION

For prompt and proper processing of your inquiries and orders, please furnish complete details of items as shown in the box below. Please feel free to call CSC's Sales Offices or Metallurgical Department, if you need any information about CSC's products or services.

Required Ordering Data		Example	
1	Specification (Name, Number, Grade)	JIS G3141 SPCC-SD CQ2 GP R35	
	Temper		A,S,8,4,2,1
	Surface Finish		Bright Finish (B)
			Matte (Dull) Finish (D)
Surface Quality	General Purposes (GP)		
	Unexposed (UE)		
2	Oiled or Non-oiled	Oiled	
3	Dimensions (Thickness×Width×Length(or coil))	1.0mm×1219mm×Coil	
4	Coil Size (Inside Diameter ' Outside Diameter)	ID 762mm ' OD 1700mm max.	
5	Mass	Max. Mass	10t max.
		Order Mass	450t
6	Applications and Fabricating Methods	Welded Pipe	
7	Special Requirements (if Required)	Hardness : 55 HRB max.	

- Remarks :
1. The contents of this catalog are for reference only-customers are urged to consult the specifications published by the corresponding associations.
  2. Information of the available steel grades, sizes, marking and packing as shown herein may be updated without notice to comply with actual production situations.
  3. We invite you to contact our Head Office should you have any questions concerning steel specifications or ordering requirements.

**Phone number are listed below for your convenience. Numbers of our international Offices are shown on the back cover.**

### 1.Sales services

#### CHINA STEEL GLOBAL TRADING CORPORATION

| Address: 10F, NO.88, Cheng gong 2nd Rd, Qian zhen, Kaohsiung 80661 TAIWAN  
 | Tel : 886-7-3322168 | Fax : 886-7-3356411 | E-mail : c00681@mail.csc.com.tw

#### CSGT JAPAN CO., LTD.

| Address:2F, Osaka U2 Bldg., 4-7 Uchihonmachi 2-Chome,Chuoku, Osaka 540-0026, Japan  
 | Tel : 002-81-6-69100850 | Fax : 002-81-6-69100851 | E-mail : gdwu@csgtjpn.co.jp

#### CSGT HONG KONG LIMITED

| Address : ROOM 1407,14/F, WORLD WIDE HOUSE, 19 DES VOEUX ROAD, CENTRAL, HONG KONG  
 | Tel : 852-25231488 | Fax : 852-25234748 | E-mail : mhliu@csgthk.com.hk

#### CSGT (SHANGHAI) CO.,LTD.

| Address : 21F, NO.1468 NAN JING WEST RD., SHANGHAI 200040  
 | Tel : 86-21-62896898 | Fax : 86-21-62896678 | E-mail : c00392@csgtsha.com

#### CSGT (SINGAPORE) PTE, LTD.

| Address : #14-01, MAS BUILDING, 10 SHENTON WAY SINGAPORE 079117  
 | Tel : 65-62238777~8 | Fax : 65-62256054 | E-mail : changcc@csgtsg.com.sg

### 2.Metallurgical Department

Technical Service Section-Metallurgy: 886-7-8021335

Metallurgical Specification and Testing Section: 886-7-8021111 Ext. 2207



### Head Office

- Address : #1, Chung Kang Rd., Hsiao Kang, Kaohsiung 81233, Taiwan, Republic of China
- Tel : 886-7-802-1111
- Fax : 886-7-802-2511 , 801-9427
- Web : [http : //www.csc.com.tw](http://www.csc.com.tw)

### China Steel Building (Group Headquarters)

- Address : #88, Chenggong 2nd Rd., Qianzhen, Kaohsiung 80661, Taiwan, Republic of China
- Tel : 886-7-337-1111
- Fax : 886-7-537-3570

### Taipei Liaison Office

- Address : Room A, 28F, #7, Sec.5, Xinyi Rd., Xinyi, Taipei 11049, Taiwan, Republic of China
- Tel : 886-2-8758-0000
- Fax : 886-2-8758-0007

### Osaka Office

- Address : 1F, Osaka U2 Bldg., 4-7Uchihonmachi 2-Chome, Chuoku , Osaka 540-0026, Japan.
- Tel : 81-6-6910-0888
- Fax : 81-6-6910-0887

### Singapore Office

- Address : # 14-01 Mas Building, 10 Shenton Way, Singapore 079117
- Tel : 65-6223-8777-8
- Fax : 65-62256054

(Manual download)

